

Compressive strength and Weibull distribution of lithium disilicate dental ceramics

by Silvia Naliani, Dahlia Sutanto, Angela Evelynna, Michael Adi Hizkia

Submission date: 26-Mar-2025 02:59PM (UTC+0700)

Submission ID: 2625645405

File name: Publikasi_Makasar_Dental_Journal.pdf (159.74K)

Word count: 2065

Character count: 11269

Compressive strength and Weibull distribution of lithium disilicate dental ceramics Kekuatan tekan dan distribusi Weibull dari keramik dental disilikat lithium

¹Silvia Naliani, ¹Dahlia Sutanto, ²Angela Evelyn, ³Michael Adi Hizkia

¹Department of Prosthodontics

²Department of Dental Materials

³Bachelor degree student

Faculty of Dentistry, Maranatha Christian University

Bandung, Indonesia

Corresponding author: Silvia Naliani, e-mail: silvia.naliani@dent.maranatha.edu

ABSTRACT

Objective: To compare the compressive strength of three types of commercial lithium disilicate ceramics. **Methods:** Three groups of lithium disilicate ceramics (IPS e.max Press, Vintage LD Press, and Celtra Press) total of twelve cylindrical specimens (diameter 4 mm x length 6 mm) were produced by laboratory processing. The compressive strength was conducted using Shimadzu universal testing machine with load cell F 50 kN, cross head speed of 1 mm/s. Micromorphology were observed using scanning electron microscope. Anova test and Weibull test were performed and $p < 0.05$ was considered significant. **Results:** There are no significant differences between three groups of lithium disilicate dental ceramics compressive strength ($p = 0.531$). However, IPS e.max Press group show higher compressive strength compared to the other two materials. IPS e.max Press and Vintage LD Press groups show significantly higher coefficient correlation than Celtra Press group. **Conclusion:** IPS e.max Press lithium disilicate dental ceramic have higher compressive strength compared to the other groups, but the reliability of Celtra Press is lower than those of lithium disilicate dental ceramics.

Keywords: dental ceramics, lithium disilicate, compressive strength, weibull

ABSTRAK

Tujuan: Untuk membandingkan kekuatan tekan dari tiga jenis keramik lithium komersial. **Metode:** Tiga kelompok keramik disilikat lithium (IPS e.max Press, Vintage LD Press, dan Celtra Press) total 12 spesimen silinder (diameter 4 mm x panjang 6 mm) diproduksi oleh pengolahan laboratorium. Kekuatan tekan dilakukan menggunakan Shimadzu Universal Testing Machine dengan load cell F 50 kN, cross head speed 1 mm/dtk. Morfologi mikro diamati menggunakan scanning electron microscope. Uji Anova dan uji Weibull dilakukan dan $p < 0,05$ dianggap signifikan. **Hasil:** Tidak ada perbedaan yang signifikan kekuatan tekan antara tiga kelompok keramik dental disilikat lithium ($p = 0,531$). Namun, IPS e.max Press group menunjukkan kekuatan tekan yang lebih tinggi dibandingkan dengan dua bahan lainnya. IPS e.max Press dan Vintage LD Press menunjukkan koefisien korelasi yang jauh lebih tinggi daripada kelompok Celtra Press. **Simpulan:** Keramik dental disilikat lithium IPS e.max Press memiliki kekuatan tekan yang lebih tinggi dibandingkan dengan kelompok yang lain, tetapi keandalan Celtra Press lebih rendah daripada keramik dental disilikat lithium.

Kata kunci: keramik dental, disilikat lithium, kekuatan tekan, Weibull

Received: 10 April 2021

Accepted: 1 August 2021

Published: 1 December 2021

INTRODUCTION

In dentistry, ceramic materials are widely used for fixed prosthodontic treatment to restore function, aesthetics and comfort.¹ All-ceramic materials can be used for single-tooth restorations such as veneers, inlays, onlays, crowns and posts. Lithium disilicate ceramic can be used for 3-unit bridges either in anterior or premolar region, whereas multi-unit bridges can be fabricated only by stabilized zirconia.²

All ceramic materials has been rapidly developed and having many advantages such as high aesthetics appearance due to optical properties especially in translucency and transparency, biocompatibility and durability, chemical inertness, low thermal conductivity, their excellent mechanical properties such as high flexural strength, fracture toughness, wear resistance and low abrasive properties.¹⁻³ The term porcelain refers to a ceramic produced by sintering a mixture of feldspar, silica, alumina, other metal oxides, pigments, and opacifying agent.^{4,5} Dental ceramics can be classified by their microstructure, processing technique, fusion temperature and clinical application.^{5,6} Mechanical and optical properties of dental ceramic depends on the nature and amount of crystalline phase.⁶ Dental ceramic have some disadvantages such as brittle nature, and fracture, and wear tendencies of antagonist teeth.^{3,6}

Lithium disilicate glass ceramic is broadly used as all ceramic restorations in dentistry due to adequate mechanical properties and the high aesthetic quality.⁷ The strength of dental ceramic depends on presence of surface ingredients, nature, amount, particle size and coefficient of thermal expansion.⁶ The composition among manufactures varies. Manufacturers adding zirconia to the ceramic system as reinforcing component.^{7,8} Zirconia-reinforced lithium silicate is glass-ceramic material enriched with highly dispersed zirconia.² The ob-

ject of this study was to compare the compressive strength of three types of commercial lithium disilicate ceramics. The compressive strength was conducted using Shimadzu universal testing machine with load cell F 50 kN, cross head speed of 1 mm/s. Micromorphology were observed using scanning electron microscope. Anova test and Weibull test were performed and $p < 0.05$ was considered significant. Results: There are no significant differences between three groups of lithium disilicate dental ceramics compressive strength ($p = 0.531$). However, IPS e.max Press group show higher compressive strength compared to the other two materials. IPS e.max Press and Vintage LD Press groups show significantly higher coefficient correlation than Celtra Press group. Conclusion: IPS e.max Press lithium disilicate dental ceramic have higher compressive strength compared to the other groups, but the reliability of Celtra Press is lower than those of lithium disilicate dental ceramics.

jective is to increase its strength.^{7,8}

There are limited study of lithium disilicate compressive strength; many studies used flexural strength, shear strength, fracture toughness and hardness to compare mechanical properties of this material.^{3,7,9,10} Compressive strength is the ability of a material to withstand 2 forces that are directed toward each other in a straight line until the material fractures.^{4,5}

Weibull distribution analysis was used to characterize the flexural strength of these materials. Weibull modulus is a parameter instrument to understanding the statistical behaviour of the strength of materials.¹¹ So, this article aims to compare the compressive strength of three types of commercial lithium disilicate ceramics

METHODS

Three commercial lithium disilicate with zirconia consist of IPS e.max Press (Ivoclar Vivadent AC), Vintage LD Press (Shofu Inc, Kyoto) and Celtra Press (Dentsply Sirona, Germany) were used in this study and produced following manufacturer instructions. Twelve specimens were prepared in cylinder of 4 mm diameter and 6 mm height. The specimens were produced with the press technique. Compressive strength was measured using universal testing machine (AGS-X series Shimadzu Japan) at a crosshead speed of 1 mm/min with 50 kN load cell until fracture occurred. The results were recorded in megapascals (MPa).

Scanning electron microscope (SEM) (JEOL JSM-6360LA) were used to analyse specimen microstructure of three lithium disilicate ceramic groups. The specimens etched using hydrofluoric acid for 90 seconds (Ultradent Porcelain Etch, USA), rinsed using water spray and dried before the scanning procedure.

The results data analysed statistically using statistical software Minitab 17 (2013 Minitab Inc). All compressive strength data were analysed using one-way Anova and Weibull distribution.

RESULTS

IPS e.max Press showed greater mean values of compressive strength (341,0 MPa) followed by Celtra Press and Vintage LD Press respectively (Table 1). One-way Anova revealed there isn't statistically significance (p -value > 0,05) among the three groups (Table 2). Weibull coefficient from 3 groups showed IPS e.max has the higher value than the others (Table 3). Figure 1, 2 and 3 showed SEM of three lithium disilicate with magnification 5000x.

Table 1 Descriptive statistic for compressive strength

Lithium disilicate group	Compressive strength mean (MPa)
IPS e.max Press	341,0 ± 59,4
Vintage LD Press	274,7 ± 26,2
Celtra Press	318,8 ± 28,5

Table 2 Result of one-way Anova

Source	F-Value	P-Value
Factor	0,68	0,531

Table 3 Distribution Weibull for compressive strength

Lithium Disilicate Group	Shape	Scale	Coefficient
IPS e.max Press	4,10	377,6	0,951
Vintage LD Press	7,19	294,2	0,935
Celtra Press	9,94	338,4	0,918

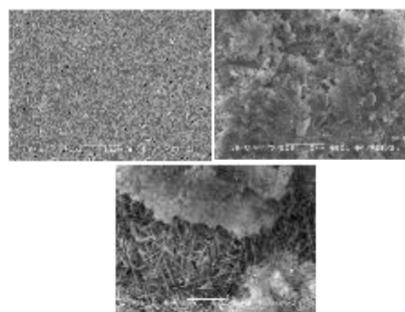


Figure 1 SEM micrograph (magnification 5000x); A IPS e.max Press, B Vintage LD Press, C Celtra Press

DISCUSSION

Recent developments of dental ceramic have led to development of crystalline porcelain with fillers such as alumina, zirconia and hydroxy apatite. Strengthening dental ceramics by reinforced the materials with a dispersed crystalline phase such as alumina or partially stabilized zirconia can strengthen the glass and improve the strength.⁶ Mechanical properties of ceramic especially glass-ceramic depend of their microstructure of their crystals.¹²

The microstructure of IPS e.max Press is crystals lithium disilicate which are embedded in a glassy matrix (Fig. 1 A), the crystal content to about 70% which translates into 30-35% glassy matrix.^{5,13} Size of IPS e.max Press lithium disilicate crystals were 1.0-4.0 µm and crystals of Vintage LD size 1.0-3.0 µm.¹⁴ Celtra Press had a high content of P₂O₅ (4.9 wt%), ZrO₂ (9.3 wt%) and lower SiO₂ compared to IPS e.max Press. IPS e.max Press had lower content of ZrO₂ and higher SiO₂ than Celtra Press.¹² Crystals distribution of Vintage LD Press (Fig. 1 B) sparser than e.max Press so the glassy matrix proportion higher and might affect the extension of cracks.¹⁴ Celtra Press (Fig. 1 C) contains about 10% zirconia besides lithium disilicate crystals, Li₂O and SiO₂, higher than IPS e.max but showed lower compressive strength compared to IPS e.max even no significant statistical differences. Both materials consist of lithium disilicate and zirconia as reinforced but different values

of compressive strength, it might have been caused by the different values of composition and crystals size. SEM micrographs showed differences in size, form and density of crystals.

Distribution Weibull is one of probability distribution for assessing the lifetime problem, in ceramic fields, this distribution has been common to indicate the brittleness of materials.¹¹ The Weibull coefficient of IPS e.max showed the higher value than the others, it

means the greater goodness of fit of this material.¹⁵ Weibull analysis is a rule to testing the strength of brittle materials.¹¹

Compressive strength test of three different ceramic materials shows that IPS e.max Press lithium disilicate dental ceramic have higher compressive strength compared to the other groups, but the reliability of Celtra Press is lower than those of lithium disilicate dental ceramics.

REFERENCES

1. Vikram V, Anon A, Reddy N. Compressive strength evaluation between metal ceramic and zirconia crowns. An in-vitro study. *Indian J Public Health Res Dev* 2020;11(1):284-9.
2. Bajraktarova-Valjakova E, Korunoska-Stevkovska V, Kapusevska B, Gigovski N, Bajraktarova-Misevska C, Grozdanov A. Contemporary dental ceramic materials, a review: chemical composition, physical and mechanical properties, indications for use. *Open Access Maced J Med Sci* 2018;6(9):1742-55.
3. Attia A, Abdelaziz KM, Freitag S, Kern M. Fracture load of composite resin and feldspathic all-ceramic CAD/CAM crowns. *J Prosthet Dent* 2006;95(2):117-23.
4. Anusavice K, Shen C, Rawls H. *Phillip's science of dental materials*. 12th Ed. Singapore: Elsevier; 2013. p.63-4.
5. McLaren PEA, Giordano R. Ceramics overview: Classification by microstructure and processing methods. *Cosmetic Dent* 2014;1:26-35.
6. Babu PJ, Alla RK, Alluri VR, Datla SR, Konakanchi A. Dental ceramics: Part I an overview of composition, structure and properties. *Am J Mater Eng Technol* 2015;3(1):13-8.
7. da Silva LH, de Lima E, Miranda RB de P, Favero SS, Lohbauer U, Cesar PF. Dental ceramics: a review of new materials and processing methods. *Braz Oral Res [Internet]*. 2017 Aug 28 [cited 2021 May 2];31(suppl 1).
8. Gracis S, Thompson V, Ferencz J, Silva N, Bonfante E. A new classification system for all-ceramic and ceramic-like restorative materials. *Int J Prosthodont* 2016;28(3):227-35.
9. Kang SH, Chang J, Son HH. Flexural strength and microstructure of two lithium disilicate glass ceramics for CAD/CAM restoration in the dental clinic. *Restor Dent Endod* 2013;38(3):134-40.
10. Nassary Zadeh P, Lümekemann N, Sener B, Eichberger M, Stawarczyk B. Flexural strength, fracture toughness, and translucency of cubic/tetragonal zirconia materials. *J Prosthet Dent* 2018;120(6):948-54.
11. Ono K. A simple estimation method of Weibull modulus and verification with strength data. *Appl Sci* 2019;9(8):1-39.
12. Hallmann L, Ulmer P, Gerngross MD, Jetter J, Mintrone M, Lehmann F, et al. Properties of hot-pressed lithium silicate glass-ceramics. *Dent Mater* 2019;35(5):713-29.
13. Datla SR, Alla RK, Alluri VR, Babu PJ, Konakanchi A. Dental ceramics: Part II-recent advances in dental ceramics. *Am J Mater Eng Technol* 2015;3(2):19-26.
14. Kameyama Y, Wada Y, Midono T, Miyake K, Kunzelmann K-H, Nihei T. Evaluation and comparison of the characteristics of three pressable lithium disilicate glass ceramic materials. *IJDR* 2017;07(11):16711-6.
15. Lee S-H. Estimation and comparison of weibull parameters for reliability assessments of Douglas-fir Wood. *IJBAS-IJENS* 2014;14(2):18-21.

Compressive strength and Weibull distribution of lithium disilicate dental ceramics

ORIGINALITY REPORT

16%	7%	9%	6%
SIMILARITY INDEX	INTERNET SOURCES	PUBLICATIONS	STUDENT PAPERS

PRIMARY SOURCES

1	Submitted to Universitas Prof. Dr. Moestopo (Beragama) Student Paper	2%
2	Burcu Ertuğ. "Mechanical performance of lithium disilicate: update on the latest experimental results", Elsevier BV, 2019 Publication	2%
3	Submitted to Fiji National University Student Paper	2%
4	Lubica Hallmann, Peter Ulmer, Mark-Daniel Gerngross, Justin Jetter, Michaël Mintrone, Frank Lehmann, Matthias Kern. "Properties of hot-pressed lithium silicate glass-ceramics", Dental Materials, 2019 Publication	1%
5	Kanji Ono. "A Simple Estimation Method of Weibull Modulus and Verification with Strength Data", Applied Sciences, 2019 Publication	1%
6	Submitted to Ajman University of Science and Technology Student Paper	1%
7	onkologia.termedia.pl Internet Source	1%

8	Internet Source	1 %
9	id.scribd.com Internet Source	1 %
10	repository.maranatha.edu Internet Source	1 %
11	www.e-jcs.org Internet Source	1 %
12	www.jstage.jst.go.jp Internet Source	1 %
13	acikbilim.yok.gov.tr Internet Source	1 %
14	Ahmad M. Al-Thobity, Abdulmohsen Alsalman. "Flexural properties of three lithium disilicate materials: An in vitro evaluation", The Saudi Dental Journal, 2020 Publication	<1 %
15	mau.diva-portal.org Internet Source	<1 %
16	www.scribd.com Internet Source	<1 %
17	Meghlaj, Mustafa. "In Vitro Evaluation of the Effect of Monobond Etch and Prime MEP Application on Shear Bond Strength and Bonding Between Resin Cement and Lithium Disilicate Glass Ceramic", Marmara Universitesi (Turkey), 2021 Publication	<1 %
18	Mullayousef, Hashem Ali. "Mechanical and Physical Properties of Three CAD/CAM Glass-Ceramics", Boston University, 2022	<1 %

19

Wolfram Höland, George Beall. "Glass-Ceramic Technology", Wiley, 2019

Publication

<1%

Exclude quotes Off

Exclude matches Off

Exclude bibliography On

Compressive strength and Weibull distribution of lithium disilicate dental ceramics

GRADEMARK REPORT

FINAL GRADE

GENERAL COMMENTS

/0

PAGE 1

PAGE 2

PAGE 3